



# DATA SHEET

# SUPRASIL







## Quartz Glass for Optics Data and Properties

 = 3D material, optically isotropic.

In quartz glass, the homogeneity is typically specified in one direction only. Heraeus manufactures quartz glass grades, which are controlled and specified in all 3 directions regarding striae, homogeneity and stress induced birefringence, for the most demanding applications. These materials are identified by the  3D symbol.

● For raw formed ingots the bubble specification is valid for the area defined by the minimum diameter tolerance. For machined parts it is defined as 100% of the material.

- Bubbles or inclusions  $\leq 0.08$  mm diameter are not counted. Tighter specification for bubbles and inclusions down to  $\leq 10\mu\text{m}$  is possible on request.
- For non-spherical bubbles the maximum dimension is used.
- The  $\Delta n$  value is the maximum permissible lateral variation in refractive index (measured by interferometer at 632.8 nm after subtraction of tilt and offset) over 90% of the diameter or edge length of a fine ground piece, or 80% of a raw formed ingot.

Grade	Bubbles and Inclusions <sup>1 2</sup>			Homogeneity <sup>6</sup>	
	The bubble grade is given for every 100 cm <sup>3</sup> . Quartzglass from Heraeus is free of inclusions.			$\Delta n$ -value <sup>4</sup>	
	DIN 58927	DIN ISO 10110 <sup>3</sup>	Total cross-sections (in mm <sup>2</sup> ) of all bubbles (TBCS value)	Striae class as <sup>5</sup> per DIN ISO 10110 (per 30 mm thickness)	PV value <sup>6</sup> (Peak-to-Valley)
Suprasil <sup>®</sup> 311 	0	1/1*0.08	$\leq 0.015$	2 / -,5	$\leq 3 \cdot 10^{-6}$
Suprasil <sup>®</sup> 312	0	1/1*0.08	$\leq 0.015$	2 / -,5	$\leq 4 \cdot 10^{-6}$
Suprasil <sup>®</sup> 313	0	1/1*0.08	$\leq 0.015$	2 / -,5	n. sp. <sup>7</sup>
Suprasil <sup>®</sup> 3001 	0	1/1*0.08	$\leq 0.015$	2 / -,5	$\leq 4 \cdot 10^{-6}$
Suprasil <sup>®</sup> 3002	0	1/1*0.08	$\leq 0.015$	2 / -,5	$\leq 10 \cdot 10^{-6}$
Suprasil <sup>®</sup> 300	0	1/1*0.08	$\leq 0.015$	acc. MIL	n. sp.
Suprasil <sup>®</sup> 3301 	0	1/1*0.08	$\leq 0.015$	2 / -,5	$\leq 2 \cdot 10^{-6}$
Suprasil <sup>®</sup> 3302	0	1/1*0.08	$\leq 0.015$	2 / -,5	$\leq 3 \cdot 10^{-6}$
Suprasil <sup>®</sup> 1 	0	1/1*0.08	$\leq 0.015$	2 / -,5	$\leq 5 \cdot 10^{-6}$
Suprasil <sup>®</sup> 2 Grade A	0	1/1*0.08	$\leq 0.015$	2 / -,5	$\leq 5 \cdot 10^{-6}$
Suprasil <sup>®</sup> 2 Grade B	0	1/1*0.08	$\leq 0.015$	2 / -,5	$\leq 10 \cdot 10^{-6}$
Suprasil <sup>®</sup> CG	0	1/1*0.08	$\leq 0.015$	acc. MIL	$\leq 30 \cdot 10^{-6}$
Suprasil <sup>®</sup> 1 ArF / KrF 	0	1/1*0.08	$\leq 0.015$	2 / -,5	$\leq 5 \cdot 10^{-6}$
Suprasil <sup>®</sup> 2 ArF / KrF	0	1/1*0.08	$\leq 0.015$	2 / -,5	$\leq 5 \cdot 10^{-6}$
Spectrosil <sup>®</sup> 2000	0	1/1*0.08	$\leq 0.015$	2 / -,5	$\leq 10 \cdot 10^{-6}$
Infrasil <sup>®</sup> 301 	0	1/1*0.16	$\leq 0.03$	2 / -,5	$\leq 5 \cdot 10^{-6}$
Infrasil <sup>®</sup> 302	0.1	1/1*0.35	$\leq 0.1$	2 / -,5	$\leq 6 \cdot 10^{-6}$
HQ <sup>®</sup> 310	2...3	1/1*0.63 $\leq 6$ kg 1/2*1.0 $> 6$ kg	0.5	n. sp.	n. sp.

■ Synthetic Fused Silica   ■ Natural Quartz <sup>8</sup>   n. sp. = not specified    = 3D material, optically isotropic

# DATA SHEET

# SUPRASIL

The maximum test diameter is 430 mm. Larger pieces are measured using overlapping interferograms.

- ⑥ Does not apply to drawn rods.
- ⑥ Lower values available on request.
- ⑦ The residual strain values refer to the measured phase difference per cm light path. The residual strain value is specified over 90% of the diameter or edge length of a fine ground piece, or 80% of a raw formed ingot.
- ⑧ Typically less than  $10 \cdot 10^{-6}$ .
- ⑨ The chemical composition, and therefore, the optical properties of natural quartz can vary.

**Refractive index**  
at 20°C and 1 bar

The given values are interpolated from measured values. More accurate data available upon request.

In contrast to other optical glasses, quartz glass shows very little difference in refractive index from melt to melt.

Residual Strain <sup>⑦</sup>  nm/cm <sup>⑧</sup>	Fluorescence	OH-Content
	Excitation by Hg-Lamp@ λ= 254 nm and UG 5-filter; Lamp-power: 8W; Detection: adapted eye	ppm (µg/g)
≤ 5	free	≤ 300
≤ 5	free	≤ 300
≤ 5	free	≤ 300
≤ 6	slight blue	≤ 1
≤ 6	slight blue	≤ 1
≤ 5	slight blue	≤ 1
≤ 2	free	≤ 20
≤ 3	free	≤ 20
≤ 5	free	≤ 1300
≤ 5	free	≤ 1300
≤ 5	free	≤ 1300
≤ 20	free	≤ 1300
≤ 5	free	≤ 1300
≤ 5	free	≤ 1300
≤ 5	free	≤ 1300
≤ 5	blue-violet	≤ 8
≤ 5	blue-violet	≤ 8
≤ 10	blue-violet	ca. 30


Wavelength nm	Suprasil®-family	Suprasil® 3001/3002/300	Infrasil® / HOQ®
ArF	190	1,5657	-
	193.4	1,5601	-
	200	1,5505	-
	202.54	-	1,5473
	220	1,5285	1,5287
	232.94	-	1,5183
	240	1,5133	1,5136
KrF	248.4	1,5083	-
	260	1,5024	1,5026
4 x Nd:YAG	266	1,4997	1,4999
	274.87	1,4961	1,4963
	280	1,4942	1,4944
	300	1,4878	1,4880
XeCl	308	1,4856	1,4858
	320	1,4827	1,4829
HeCd	325	1,4816	1,4818
N2	337	1,4792	1,4794
	340	1,4787	1,4788
	360	1,4753	1,4754
(ni)	365.48	1,4745	1,4748
	380	1,4725	1,4728
	400	1,4701	1,4704
(nh)	404.65	1,4696	1,4699
(ng)	435.83	1,4667	1,4668
HeCd	441.6	1,4662	1,4665
Kr	447.1	1,4658	1,4659
(nF)	486.13	1,4631	1,4634
Ar	488	1,4630	1,4633
	514.5	1,4616	1,4619
2 x Nd:YAG	532	1,4607	1,4610
(ne)	546.07	1,4601	1,4604
(nd)	587.56	1,4585	1,4588
HeNe	632.8	1,4570	1,4573
(nc)	656.27	1,4564	1,4567
Ruby	694.3	1,4554	1,4557
Kr	752.5	1,4542	1,4545
	800	1,4533	1,4536
	850	1,4525	1,4528
	900	1,4518	1,4520
GaAs	905	1,4517	1,4518
	1000	1,4504	1,4507
Nd:YAG	1064	1,4496	1,4499
HeNe	1153	1,4486	1,4489
	1200	1,4481	1,4483
Nd:YAG	1319	1,4467	1,4470
	1400	1,4458	1,4461
	1600	1,4434	1,4437
	1800	1,4409	-
	2000	1,4381	-
	2200	1,4350	-
	2400	1,4316	-
	2600	1,4279	-
	2800	1,4238	-
	3000	1,4193	-
	3200	1,4143	-
	3400	1,4088	-

# DATA SHEET

# SUPRASIL


## Optical Homogeneity and Stress Induced Birefringence

The false colour diagram below shows the typical two-dimensional refraction-index distribution. The interferogram belongs to a circular blank.

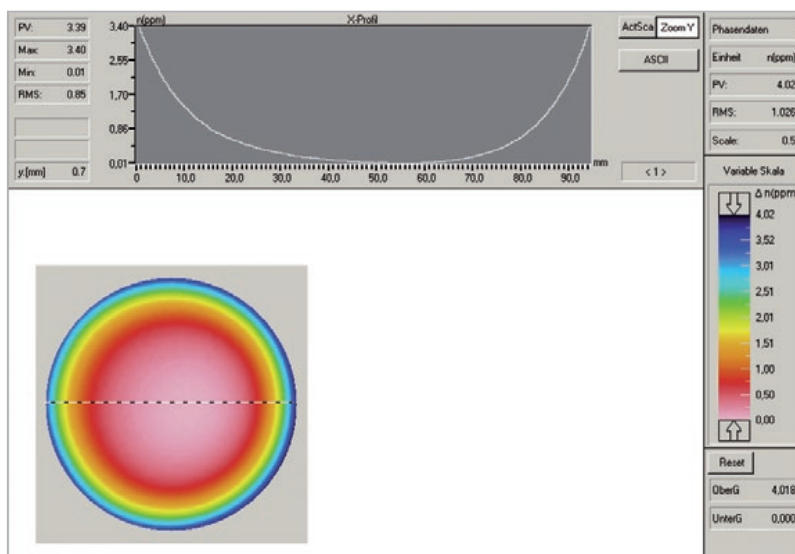

The sectional view along the diameter shows the refraction-index distribution across the blank. One can clearly see the very low value in the center of the plate and the rise close to the edge.

The false colour diagram below shows the typical two-dimensional birefringence distribution.

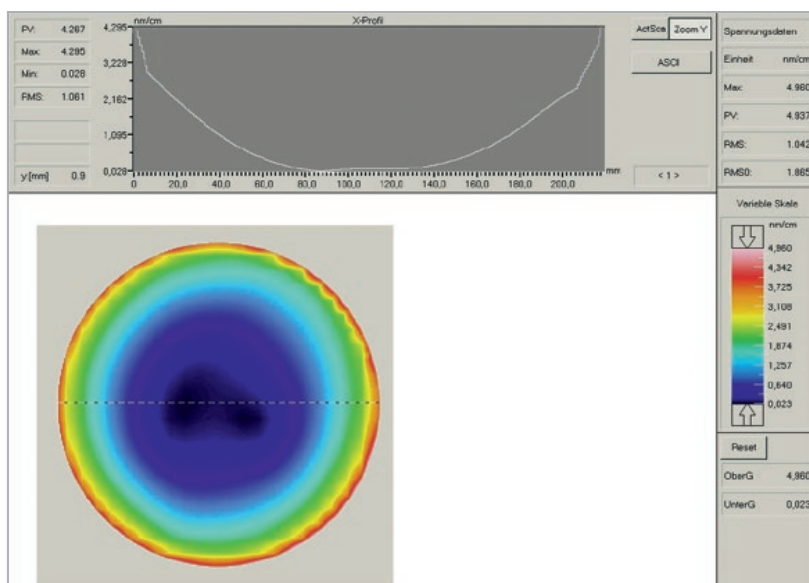


The sectional view along the diameter shows the birefringence distribution across the plate. One can clearly see the very low value in the center of the plate and the rise close to the edge.

# DATA SHEET


# SUPRASIL

## Typical transmission including Fresnel reflection losses $(1-R)^2$


Suprasil® 311, 312, 313  
Suprasil® 3001, 3002, 300  
Suprasil® 3301, 3302

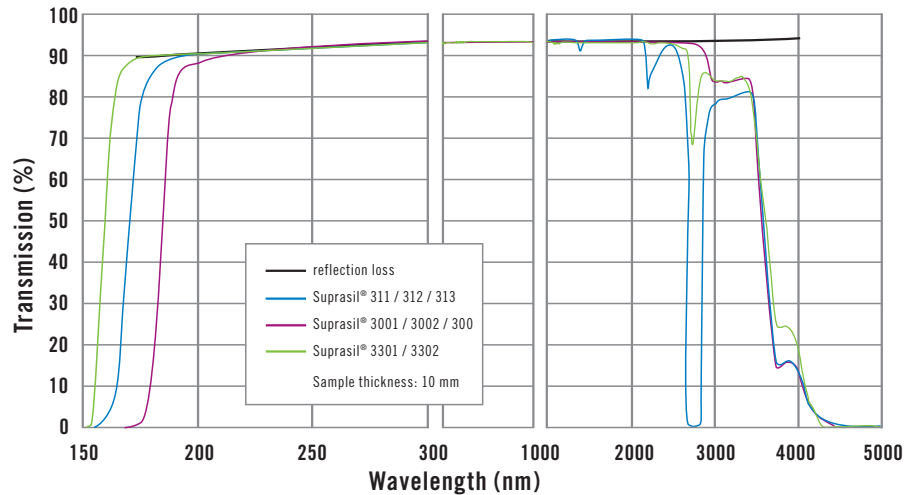

Suprasil® 1, 1 ArF / KrF  
Suprasil® 2 Grade A, 2 ArF / KrF  
Suprasil® 2 Grade B, Suprasil® CG  
Spectrosil® 2000

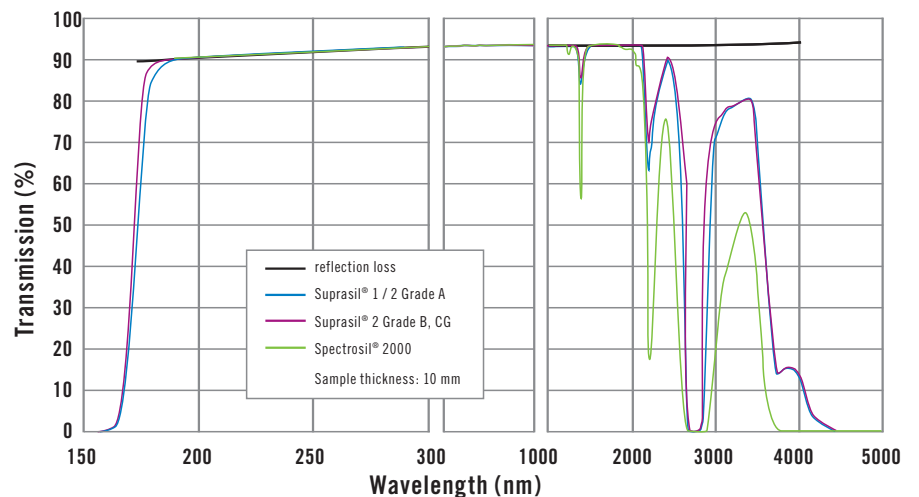

HOQ® 310  
Infrasil® 301, 302

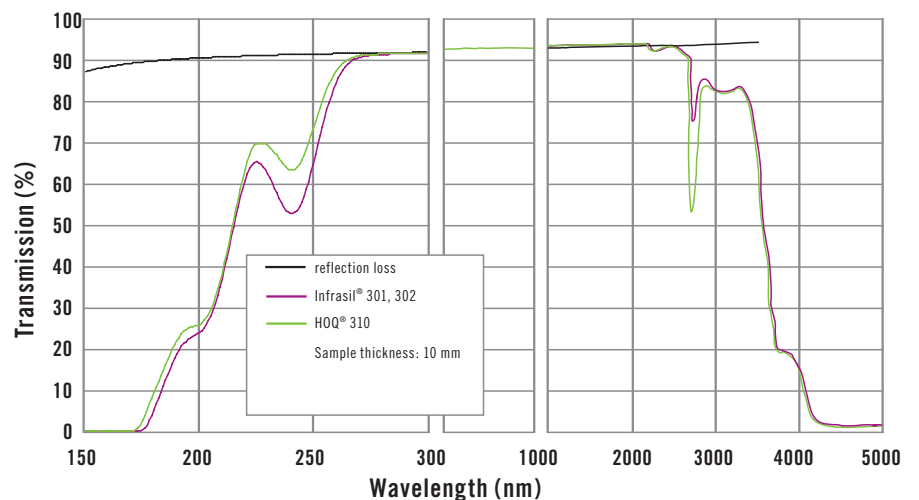

The uppermost curves in the transmission graphs indicate the calculated Fresnel reflection losses for two uncoated surfaces.

Please find our transmission calculator online at [www.herae.us/transmission-calculator](http://www.herae.us/transmission-calculator)

## DATA SHEET

## SUPRASIL

### Technical Properties

#### Internal transmission (%)

Values of pure transmissions of a 10 mm thick sample for selected UV-Wavelengths.

Wavelength nm	Suprasil® ArF/ KrF	Suprasil®- family
	- specified -	- typical -
193,4	≥ 99,30	98,50
248,4	≥ 99,80	99,50
266	99,90	99,90

#### Relative temperature coefficients of the refractive index in 10<sup>-6</sup> K<sup>-1</sup>

Wave-length nm	Suprasil®-family, Spectrosil®		Infrasil® / HOQ®	
	0...20°C	20...40°C	0...20°C	20...40°C
237,8	14,6	14,9	15,2	15,3
365	11	11,2	11,5	11,6
546,1	9,9	10,1	10,6	10,7
587,6	9,8	10,0	10,5	10,6
643,8	9,6	9,8	10,4	10,5

#### Abbe constant

$v_d = \frac{n_d - 1}{n_f - n_c}$	67,8 ± 0,5
-----------------------------------	------------

#### Birefringence constant @ 633 nm

$\frac{\text{nm}}{\text{cm} \cdot \text{bar}}$	3,54 ± 0,05	3,61 ± 0,05
--	-------------	-------------

#### Refraction index dispersion

Dispersion constants (Sellmeier)

	Suprasil®-family, Spectrosil®	Infrasil® / HOQ®
B1	4,73115591 · 10 <sup>-1</sup>	4,76523070 · 10 <sup>-1</sup>
B2	6,31038719 · 10 <sup>-1</sup>	6,27786368 · 10 <sup>-1</sup>
B3	9,06404498 · 10 <sup>-1</sup>	8,72274404 · 10 <sup>-1</sup>
C1	1,29957170 · 10 <sup>-2</sup>	2,84888095 · 10 <sup>-3</sup>
C2	4,12809220 · 10 <sup>-3</sup>	1,18369052 · 10 <sup>-2</sup>
C3	9,87685322 · 10 <sup>1</sup>	9,56856012 · 10 <sup>1</sup>

#### Sellmeier Equation:

$$n^2 - 1 = B_1 \lambda^2 / (\lambda^2 - C_1) + B_2 \lambda^2 / (\lambda^2 - C_2) + B_3 \lambda^2 / (\lambda^2 - C_3)$$

Wavelength  $\lambda$  in  $\mu\text{m}$  at 20°C

#### Typical trace impurities in quartz glass

Impurities	Suprasil®-family, Spectrosil®	Infrasil® / HOQ®
	ppm	ppm
Al = aluminium	≤ 0,010	20
Ca = calcium	≤ 0,015	1
Cr = chrome	≤ 0,001	0,1
Cu = copper	≤ 0,003	0,1
Fe = iron	≤ 0,005	0,8
K = potassium	≤ 0,010	0,8
Li = lithium	≤ 0,001	1
Mg = magnesium	≤ 0,005	0,1
Na = sodium	≤ 0,010	1
Ti = titanium	≤ 0,005	1

# DATA SHEET

# SUPRASIL

Mechanical data		Suprasil®-family, Spectrosil® Infrasil®/HOQ®
Density	g/cm <sup>3</sup>	2,20
Mohs-hardness		5,5.....6,5
Micro-hardness	N/mm <sup>2</sup>	8600.....9800
Knoop-hardness	N/mm <sup>2</sup>	5800.....6200
Modulus of elasticity (at 20°C)	N/mm <sup>2</sup>	7,0 · 10 <sup>4</sup>
Modulus of torsion	N/mm <sup>2</sup>	3 · 10 <sup>4</sup>
Poisson's ratio		0,17
Compressive strength	N/mm <sup>2</sup>	1150
Tensile strength	N/mm <sup>2</sup>	50
Bending strength	N/mm <sup>2</sup>	67
Torsional strength	N/mm <sup>2</sup>	30
Sound velocity	m/s	5720

Electrical data		
<b>Resistivity in Ω·m</b>		
20°C		10 <sup>16</sup>
400°C		10 <sup>8</sup>
800°C		6,3 · 10 <sup>4</sup>
1200°C		1,3 · 10 <sup>3</sup>
<b>Dielectric strength in kV/mm (Layer thickness ≥ 5 mm)</b>		
20°C		40...50
500°C		4...5
<b>Dielectric loss angle (tg δ)</b>		
1kHz		0,0005
1...1000MHz		< 0,001
3 · 10 <sup>4</sup> MHz		0,0004
<b>Dielectric constant (ε)</b>		
20°C	0...1 MHz	3,7
23°C	0...1000 MHz	3,80
23°C	3 · 10 <sup>4</sup> MHz	3,81

Thermal data		Suprasil®- Family, Spectrosil®	Infrasil®/ HOQ®
Softening temperature	°C	~ 1600	~ 1730
Annealing temperature	°C	~ 1120	~ 1180
strain temperature	°C	~ 1025	~ 1075
<b>Max. working temperature</b>			
continuous	°C	~ 950	~ 1150
short-term	°C	~ 1200	~ 1300
<b>Mean specific heat J/kg · K</b>			
	0...100°C	772	
	0...500°C	964	
	0...900°C	1052	
<b>Heat conductivity W/m · K</b>			
	20°C	1,38	
	100°C	1,46	
	200°C	1,55	
	300°C	1,67	
	400°C	1,84	
	950°C	2,68	
<b>Mean thermal expansion coefficient K<sup>-1</sup></b>			
	-160...0°C	0	
	-50...0°C	2,7 · 10 <sup>-7</sup>	
	0...100°C	5,1 · 10 <sup>-7</sup>	
	0...200°C	5,8 · 10 <sup>-7</sup>	
	0...300°C	5,9 · 10 <sup>-7</sup>	
	0...600°C	5,4 · 10 <sup>-7</sup>	
	0...900°C	4,8 · 10 <sup>-7</sup>	